

TECHNICAL REPORT ARCCB-TR-97016

**MODIFICATION OF ASTM STANDARD E1681
ON ENVIRONMENTAL CRACKING TO INCLUDE
BOLT-LOAD SPECIMEN TESTING**

**J. H. UNDERWOOD
W. A. VAN DER SLUYS
G. N. VIGILANTE**

JULY 1997



**US ARMY ARMAMENT RESEARCH,
DEVELOPMENT AND ENGINEERING CENTER
CLOSE COMBAT ARMAMENTS CENTER
BENÉT LABORATORIES
WATERVLIET, N.Y. 12189-4050**



APPROVED FOR PUBLIC RELEASE; DISTRIBUTION UNLIMITED

19970806 096

EXC QUALITY IMPROVED

DISCLAIMER

The findings in this report are not to be construed as an official Department of the Army position unless so designated by other authorized documents.

The use of trade name(s) and/or manufacturer(s) does not constitute an official indorsement or approval.

DESTRUCTION NOTICE

For classified documents, follow the procedures in DoD 5200.22-M, Industrial Security Manual, Section II-19 or DoD 5200.1-R, Information Security Program Regulation, Chapter IX.

For unclassified, limited documents, destroy by any method that will prevent disclosure of contents or reconstruction of the document.

For unclassified, unlimited documents, destroy when the report is no longer needed. Do not return it to the originator.

REPORT DOCUMENTATION PAGE			Form Approved OMB No. 0704-0188	
Public reporting burden for this collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing the collection of information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing this burden, to Washington Headquarters Services, Directorate for Information Operations and Reports, 1215 Jefferson Davis Highway, Suite 1204, Arlington, VA 22202-4302, and to the Office of Management and Budget, Paperwork Reduction Project (0704-0188), Washington, DC 20503.				
1. AGENCY USE ONLY (Leave blank)		2. REPORT DATE July 1997		3. REPORT TYPE AND DATES COVERED Final
4. TITLE AND SUBTITLE MODIFICATION OF ASTM STANDARD E1681 ON ENVIRONMENTAL CRACKING TO INCLUDE BOLT-LOAD SPECIMEN TESTING				5. FUNDING NUMBERS AMCMS No. 6111.02.H611.1
6. AUTHOR(S) J.H. Underwood, W.A. VanDerSluys (Babcock and Wilcox, Alliance, OH), and G.N. Vigilante				
7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES) U.S. Army ARDEC Benet Laboratories, AMSTA-AR-CCB-O Watervliet, NY 12189-4050				8. PERFORMING ORGANIZATION REPORT NUMBER ARCCB-TR-97016
9. SPONSORING / MONITORING AGENCY NAME(S) AND ADDRESS(ES) U.S. Army ARDEC Close Combat Armaments Center Picatinny Arsenal, NJ 07806-5000				10. SPONSORING / MONITORING AGENCY REPORT NUMBER
11. SUPPLEMENTARY NOTES				
12a. DISTRIBUTION AVAILABILITY STATEMENT Approved for public release; distribution unlimited.				12b. DISTRIBUTION CODE
13. ABSTRACT (Maximum 200 words) Benet Laboratories experience with environmental cracking of cannon components has been combined with the technical expertise of various participants at ASTM technical meetings and symposia to develop a modification to ASTM Standard E1681, "Test Method for Determining a Threshold Stress Intensity Factor for Environment-Assisted Cracking of Metallic Materials Under Constant Load." A bolt-loaded compact specimen has been added to the standard to allow constant displacement bolt-load tests of environmental cracking threshold. Recent investigations of environmental cracking in two cannon systems are briefly summarized, including cracking in acids used in the electroplating process and cracking due to cannon propellant gases. The modified draft of ASTM Standard E1681 is presented, including the additions to test procedure, apparatus, and stress intensity factor expressions required to perform bolt-load tests of environmental cracking threshold.				
14. SUBJECT TERMS Environmental Cracking, Fracture Mechanics, High Strength Steels, Bolt-Load Specimen, Standardized Tests, Cracking Threshold				15. NUMBER OF PAGES 29
				16. PRICE CODE
17. SECURITY CLASSIFICATION OF REPORT UNCLASSIFIED	18. SECURITY CLASSIFICATION OF THIS PAGE UNCLASSIFIED	19. SECURITY CLASSIFICATION OF ABSTRACT UNCLASSIFIED	20. LIMITATION OF ABSTRACT UL	

TABLE OF CONTENTS

	<u>Page</u>
INTRODUCTION	1
PROPOSED ADDITION TO E 1681	2
1.0 Scope	2
2.0 Referenced Documents	2
3.0 Terminology	3
4.0 Summary of Test Method	4
5.0 Significance, Precautions, and Use	5
6.0 Apparatus	7
7.0 Specimen Configuration, Size, and Preparation	9
8.0 General Procedure	11
9.0 Calculations and Interpreting Results	15
10.0 Report	17
11.0 Precision and Bias	18
12.0 Keywords	19
DISCUSSION AND CLOSING	26
REFERENCES	27

LIST OF ILLUSTRATIONS

1.	Typical Configuration of a Dead-Weight Cantilever-Beam Loading Fixture	21
2.	Tension Test Clevis Design	21
3.	Typical Test Arrangement for Constant Displacement K_{IEAC} Tests with Modified Bolt-Load Compact Specimen; $H/W = 0.486$	22

4.	Beam Specimen	23
5.	Standard Proportions and Tolerances for the Compact Specimen	23
6.	Standard Configuration for the Modified Bolt-Load Compact Specimen; H/W = 0.486	24
7.	Crack Starter Notch and Fatigue Crack Configurations	25

INTRODUCTION

The main impetus for Army interest in environmental cracking tests was a striking failure in which a crack ran for a distance of 1.6 m in a cannon under no external loads. Major factors that led to the failure include:

- Use of A723 high strength steel (1207 MPa yield strength) in the presence of sustained tensile (residual) stresses
- Use of strong acids for electropolishing before electroplating

Details of this failure are described in Reference 1. It was immediately clear that tests of resistance to environmental cracking under these conditions were necessary in order to understand and control failures of this type. Review of the technical literature showed that the classic bolt-load specimen approach of Wei and Novak (ref 2) would be very useful, but their work had not yet been included in any standard test procedure. Pointing this out at a meeting of ASTM Technical Committee E08 on Fatigue and Fracture quickly resulted in an Army-led task to propose the inclusion of bolt-load tests in the recently adopted ASTM Standard E1681, "Test Method for Determining a Threshold Stress Intensity Factor for Environment-Assisted Cracking of Metallic Materials Under Constant Load" (ref 3). A constant displacement test such as the bolt-load specimen would provide a useful complement to the constant load tests in ASTM Standard E1681.

Another series of failures in cannon components has recently been recognized as environmental cracking controlled (ref 4). Troiano and coworkers investigated several fatigue cracking scenarios in a prototype cannon in an unsuccessful attempt to explain the failures as fatigue controlled. Their results suggest that environmental cracking of A723 high strength steel (1160 MPa yield strength) in the presence of sustained tensile stress at a seal and hydrogen-containing propellant gases caused the failures.

A summary of bolt-load environmental cracking threshold tests that have been performed in response to environmental cracking failures in cannons has recently been written by Vigilante and coworkers (ref 5). The materials tested were A723, Maraging 200, and PH 13-8 Mo steels and Alloy 718, Alloy 706, and A286 nickel-iron base alloys, in both acid and electrolytic cell environments. One important conclusion drawn from the tests was that A723 steel in the 1160 to 1200 yield strength range is extremely susceptible to environmental cracking in hydrogen environments. General features of the bolt-load tests were their good repeatability, the long test times required for the iron-nickel base alloys, and the importance of exposing the test samples to the environment *before* application of the test load. The tests provided an excellent technical basis for the development of the bolt-load specimen addition to ASTM Standard E1681, in combination with the experience of several participants in ASTM Committee E08 meetings and symposia. The draft of the proposed addition is given next, in the format used with ASTM standards, followed by discussion of key points and closing remarks.

PROPOSED ADDITION TO E 1681

Standard Test Method for Determining a Threshold Stress Intensity Factor for Environment-Assisted Cracking of Metallic Materials Under Constant Load

1.0 SCOPE

1.1 This test method covers the determination of the environment-assisted cracking threshold stress intensity factor parameters, K_{IEAC} and K_{EAC} , for metallic materials from constant-load testing of fatigue precracked beam or compact fracture specimens and from constant-displacement testing of fatigue precracked bolt-load compact fracture specimens.

1.2 This test method is applicable to environment-assisted cracking in aqueous or other aggressive environments.

1.3 Materials that can be tested by this method are not limited by thickness or by strength as long as specimens are of sufficient thickness and planar size to meet the size requirements of this standard.

1.4 A range of specimen sizes with proportional planar dimensions is provided, but size may be variable and adjusted for yield strength and applied load. Specimen thickness is a variable independent of planar size.

1.5 Specimen configurations other than those contained in this test method may be used, provided that well-established stress intensity calibrations are available and that specimen dimensions are of sufficient size to meet the size requirements of this standard during testing.

1.6 This standard may involve hazardous materials, operations, and equipment and does not purport to address all of the safety problems associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and to determine the applicability of regulatory limitations prior to use.

2.0 REFERENCED DOCUMENTS

2.1 ASTM Standards:

D 1129	Definitions of Terms Relating to Water ¹
D 1141	Specifications for Substitute Ocean Water ²
E 4	Standard Practices for Load Verification of Testing Machines ³
E 8	Test Methods of Tension Testing of Metallic Materials ³
E 399	Test Method for Plane-Strain Fracture Toughness of Metallic Materials ³

¹Annual Book of ASTM Standards, Vol 11.01.

²Annual Book of ASTM Standards, Vol 11.02.

³Annual Book of ASTM Standards, Vol 03.01.

E 616	Terminology Relating to Fracture Testing ³
E 647	Test Method for Measurement of Fatigue Crack Growth Rates ³
G 1	Practice for Preparing, Cleaning, and Evaluating Corrosion Test Specimens ⁴
G 3	Practice for Conventions Applicable to Electrochemical Measurements in Corrosion Testing ⁴
G 5	Standard Reference Method for Making Potentiostatic and Potentiodynamic Anodic Polarization Measurements ⁴
G 15	Terminology Relating to Corrosion and Corrosion Testing ⁴

3.0 TERMINOLOGY

3.1 Terminology related to fracture testing given in Standard E 616 and terms related to corrosion testing given in Standard G 15 are applicable to this test method.

3.2 Definitions:

3.2.1 **Stress-corrosion cracking, SCC**—a cracking process that requires the simultaneous action of a corrodent and sustained tensile stress.

3.2.2 **Stress intensity factor threshold for plane strain environment-assisted cracking, $K_{IEAC}[FL^{-3/2}]$** —the highest value of the stress intensity factor (K) at which crack growth is not observed for a specified combination of material and environment and where the specimen size is sufficient to meet requirements for plane strain as described in ASTM E 399.

3.2.3 **Stress intensity factor threshold for environment-assisted cracking, $K_{EAC}[FL^{-3/2}]$** —the highest value of the stress intensity factor (K) at which crack growth is not observed for a specified combination of material and environment and where the measured value may depend on specimen thickness.

3.2.4 **Physical crack size, $a_p[L]$** —the distance from a reference plane to the observed crack front. This distance may represent an average of several measurements along the crack front. The reference plane depends on the specimen form, and it is normally taken to be either the boundary, or a plane containing either the loadline or the centerline of a specimen or plate. The reference plane is defined prior to specimen deformation.

3.2.5 **Original crack size, $a_o[L]$** —the physical crack size at the start of testing.

3.2.6 **Original uncracked ligament, $b_o[L]$** —distance from the original crack front to the back edge of the specimen ($b_o = W - a_o$).

3.2.7 **Specimen thickness, $B[L]$** —the side-to-side dimension of the specimen being tested.

⁴Annual Book of ASTM Standards, Vol 03.02.

3.2.8 Tensile strength, $\sigma_{TS}[FL^{-2}]$ —the maximum tensile stress that a material is capable of sustaining. Tensile strength is calculated from the maximum load during a tension test carried to rupture and the original cross-section area of the specimen.

3.3 Description of Terms Specific to This Standard:

3.3.1 Environment-assisted cracking, *EAC*—a cracking process in which the environment promotes crack growth or higher crack growth rates than would occur without the presence of the environment.

3.3.2 Normalized crack size, a/W —the ratio of crack size, a , to specimen width, W . Specimen width is measured from a reference position such as the front edge in a bend specimen or the loadline in the compact specimen to the back edge of the specimen.

3.3.3 Yield strength, $\sigma_{YS}[FL^{-2}]$ —the stress at which a material exhibits a specific limiting deviation from the proportionality of stress to strain. This deviation is expressed in terms of strain.

Note 1—In this standard test method, the yield strength determined by the 0.2% offset method is used.

3.3.4 Effective yield strength, $\sigma_Y[FL^{-2}]$ —an assumed value of uniaxial yield strength that represents the influences of plastic yielding upon fracture test parameters. For use in this test method it is calculated as the average of the 0.2% offset yield strength, σ_{YS} , and the ultimate tensile strength, σ_{TS} , or

$$\sigma_Y = (\sigma_{YS} + \sigma_{TS})/2$$

3.3.5 Notch length, $a_n(L)$ —the distance from a reference plane to the front of the machined notch. The reference plane depends on the specimen form, and normally is taken to be either the boundary, or a plane containing either the loadline or the centerline of a specimen or plate. The reference plane is defined prior to specimen deformation.

4.0 SUMMARY OF TEST METHOD

4.1 This test method involves testing of single-edge notched [*SE(B)*] specimens, or compact [*C(T)*] specimens, or bolt-load compact [*MC(W)*] specimens, precracked in fatigue. The single-edge notched specimen is tested in cantilever bending. An environmental chamber is either attached to the specimen or the specimen is contained within the chamber. The chamber must enclose the portion of the specimen where the crack tip is located. Prescribed environmental conditions must be established and maintained within the chamber at all times during the test.

4.1.1 Specimens shall be deadweight loaded or otherwise held under constant load or held under constant displacement (defined in Section 6.2) for a prescribed length of time, during which failure by crack growth leading to fracture may or may not occur. K_{IEAC} and K_{EAC} are defined as the highest value of stress intensity factor at which neither failure nor crack growth occurs. The stress intensity factor (K) is calculated from an expression based on linear elastic

stress analysis. To establish a suitable crack-tip condition for constant load tests, the stress-intensity level at which the fatigue precracking of the specimen is conducted is limited to a value substantially less than the measured K_{IEAC} or K_{EAC} values. For constant displacement tests, the stress-intensity level at which the fatigue precracking of the specimen is conducted is limited to the requirements of Test Method for Plane-Strain Fracture Toughness of Metallic Materials (ASTM E 399). The validity of the K_{IEAC} value determined by this test method depends on meeting the size requirements to ensure plane strain conditions, as stated in Test Method E 399. The validity of the K_{EAC} value depends on meeting the size requirements for linear elastic behavior, as stated in the Test Method for Fatigue Crack Growth Rates (E 647).

4.1.2 This test method can produce information on the onset of environment-assisted crack growth. Crack growth rate information can be obtained after crack nucleation, but the method for obtaining this information is not part of this test method.

4.2 The mechanisms of environment-assisted cracking are varied and complex. Measurement of a K_{EAC} or K_{IEAC} value for a given combination of material and environment provides no insight into the particular cracking mechanism that was either operative or dominant. Two prominent theories of environment-assisted cracking are anodic reaction and hydrogen embrittlement (ref 1). The data obtained from this test method may be interpreted by either theory of environment-assisted cracking.

4.3 Specimen thickness governs the proportions of plane strain and plane stress deformation local to the crack tip, along with the environmental contribution to cracking. Since these chemical and mechanical influences cannot be separated in some material/environment combinations, thickness must be treated as a variable. In this method, however, the stress in the specimen must remain elastic. For these reasons two threshold values of EAC are defined by this test method. The measurement of K_{IEAC} requires that the thickness requirements of plane strain constraint are met. The less restrictive requirements of K_{EAC} are intended for those conditions in which the results are a strong function of the thickness of the specimen and the application requires the testing of specimens with thickness representative of the application.

4.4 A variety of environmental (temperature, environment composition, and electrode potential, for example) and metallurgical (yield strength, alloy composition, and specimen orientation) variables affect K_{EAC} and K_{IEAC} .

5.0 SIGNIFICANCE, PRECAUTIONS, AND USE

5.1 The parameters K_{EAC} or K_{IEAC} determined by this test method characterize the resistance to crack growth of a material with a sharp crack in specific environments under loading conditions in which the crack-tip plastic region is small compared with the crack depth and the uncracked ligament. The less restrictive thickness requirements of K_{EAC} are intended for those conditions in which the results are a strong function of the thickness of the specimen and the application requires the testing of specimens with thickness representative of the application. Since the chemical and mechanical influences cannot be separated, in some material/environment combinations, the thickness must be treated as a variable. A K_{EAC} or K_{IEAC} value is believed to represent a characteristic measurement of environment-assisted cracking resistance in a precracked specimen exposed to an environment under sustained tensile loading. A K_{EAC} or K_{IEAC} value may be used to estimate the relationship between failure stress and defect size for a material under any service condition, where the combination of crack-like defects, sustained

tensile loading, and the same specific environment would be expected to occur. (Background information concerning the development of this test method can be found in References 2 through 17).

5.1.1 The apparent K_{EAC} or K_{IEAC} of a material under a given set of chemical and electrochemical environmental conditions is a function of the test duration. It is difficult to furnish a rigorous and scientific proof for the existence of a threshold (refs 3,4). Therefore, application of K_{EAC} or K_{IEAC} data in the design of service components should be made with awareness of the uncertainty inherent in the concept of a true threshold for environment-assisted cracking in metallic materials (refs 5,17). A measured K_{EAC} or K_{IEAC} value for a particular combination of material and environment may, in fact, represent an acceptably low rate of crack growth rather than an absolute upper limit for crack stability. Care should be exercised when service times are substantially longer than test times.

5.1.2 The degree to which load deviations from static tensile stress will influence the apparent K_{EAC} or K_{IEAC} of a material is largely unknown. Small-amplitude cyclic loading, well below that needed to produce fatigue crack growth, superimposed on sustained tensile loading was observed to significantly lower the apparent threshold for stress corrosion cracking in certain instances (refs 6,7). Therefore, caution should be used in applying K_{EAC} or K_{IEAC} data to service situations involving cyclic loading. In addition, since this test standard is for static loading, small-amplitude cyclic loading should be avoided during testing.

5.1.3 In some material/environment combinations the smaller the specimen the lower the measured K_{EAC} value, while in other material/environment combinations the measured K_{IEAC} value will be the lowest value (refs. 4,8-12). If for the material/environment combination of interest it is not known which specimen size will result in the lower measured value, then it is suggested that the use of both specimen sizes should be considered; that is, specimens with thicknesses representative of the application and specimens in which the thickness meets the requirements (7.2.1.1) of a K_{IEAC} value.

5.1.3.1 The user may optionally determine and report a K_{EAC} value or a K_{IEAC} value. The specimen size validity requirements for a K_{EAC} value meet the size requirements developed for Test Method E 647 to achieve predominately elastic behavior in the specimen. The Test Method E 647 size requirements for compact specimens should be applied to both the compact specimen and the beam specimen. The specimen size validity requirements for a K_{IEAC} value meet the size requirements developed for plane strain conditions for Test Method E 399.

5.1.4 Evidence of environment-assisted crack growth under conditions that do not meet the validity requirements of Section 7.2 may provide an important indication of susceptibility to environmental cracking but cannot be used to determine a valid K_{EAC} value (ref 13).

5.1.5 Environment-assisted cracking is influenced by both mechanical and electrochemical driving forces. The latter can vary with crack depth, opening, or shape and may not be uniquely described by the fracture mechanics stress intensity factor. As an illustrative example, note the strong decrease reported in K_{ISCC} ⁵ with decreasing crack size below 5 mm for steels in 3% NaCl in water solution (ref 14). Geometry effects on K similitude should be experimentally assessed

⁵ K_{ISCC} has been used in the literature as a special case of K_{IEAC} in which the crack growth is known to be due to the simultaneous action of a stress and a corrodent.

for specific material/environment systems. Application modeling based on K_{EAC} similitude should be conducted with caution when substantial differences in crack and specimen geometry exist between the specimen and the component.

5.1.6 Not all combinations of material and environment will result in environment-assisted cracking. In general, susceptibility to aqueous stress-corrosion cracking decreases with decreasing material strength level. When a material in a certain environment is not susceptible to environment-assisted cracking, it will not be possible to measure K_{EAC} or K_{IEAC} . This test method can serve the following purposes:

5.1.6.1 In research and development, valid K_{EAC} or K_{IEAC} data can quantitatively establish the effects of metallurgical and environmental variables on the environment-assisted cracking resistance of materials.

5.1.6.2 In service evaluation, valid K_{EAC} or K_{IEAC} data can be utilized to establish the suitability of a material for an application with specific stress, flaw size, and environmental conditions.

5.1.6.3 In acceptance and quality control specifications, valid K_{EAC} or K_{IEAC} data can be used to establish criteria for material processing and component inspection.

5.1.7 Some material/environment combinations with the constant displacement bolt-load compact specimen test can result in load relaxation that will affect the test results. For relatively low strength material, non-aggressive environments, or high test temperatures, load relaxation can occur independently from environment-assisted cracking. A significant load relaxation would make any cracking results difficult to interpret. If a significant load relaxation is believed to be possible, the following trial specimen test is recommended. Test a trial specimen with all the test conditions of interest, except with no environment applied. Monitor the load on the sample using a bolt with an electronic load cell attached. Instrumented bolts of this type are commercially available. A load relaxation of more than 5% after 24 hours indicates that the constant displacement test method may not be suitable for these test conditions, and a constant load test should be considered.

6.0 APPARATUS

6.1 Fixtures

6.1.1 Cantilever Beam Specimens—Specimens should be loaded with one end clamped in a stable rigid fixture and the other end clamped to a horizontal moment arm to which a load is applied. In a fixture of this type, the long axis of the specimen is placed horizontally with the notch opening upward. A schematic representation of a suitable loading fixture is given in Fig. 1. Note that limits are placed on the proximity of fixture contact points to the specimen notch and on the length of the moment arm. The fixture should have enough stiffness to ensure that moment arm deflection under load is primarily caused by test specimen compliance. In situations where a single loading fixture simultaneously accommodates multiple specimens, it is important that the loading fixture be rigid enough to minimize transmission of transient loading deflections from specimen to specimen through the fixture.

6.1.2 Compact Specimens—A loading clevis suitable for constant load testing of compact specimens is shown in Fig. 2. Both ends of the specimen are held in a clevis and loaded through pins to allow rotation of the specimen during testing. To provide rolling contact between the loading pins and the clevis holes, the holes are machined with small flats on the loading surface. Other clevis designs may be used if it can be demonstrated that they will accomplish the same result.

6.1.3 Bolt-Load Compact Specimens—A test arrangement suitable for constant-displacement testing of bolt-load compact specimens is shown in Fig. 3. The displacement is applied to the specimen containing a machined notch and fatigue precrack. The displacement is applied with a bolt tightened against a flattened pin and measured with an electronic crack-mouth-opening-displacement (CMOD) gage (see Test Method E 399). Reference marks on the face of the specimen on both sides of the notch may also be used to verify the CMOD measurement of the applied displacement. The gage is attached to the specimen using integral knife edges machined into the specimen or using knife edges affixed to the specimen. Other types of gages and attachments may be used if it can be demonstrated that they will accomplish the same result. It is recommended that, if possible, the bolt pin be isolated from the environment and that an electric insulator be used between the bolt and pin. For some test conditions, environmental isolation and electrical insulation may not be possible.

6.2 Load or Displacement Application

6.2.1 Constant-Load Specimens—Specimens must be deadweight loaded or loaded so that the load remains constant throughout the test. Weights or a servo-controlled actuator are suitable for this purpose. A means must be provided to accurately measure the load, including the weight of the moment arm and associated load train fixtures. This may be done by including an electronic load cell in the load train or by using calibrated weights. The load applied to the specimen must be known, with an accuracy of $\pm 1\%$ of the indicated reading. Overloads of more than 3% and repetitive load fluctuations of more than 1% must be avoided during the experiment. In addition, it is important that extraneous bending and torsional loads be kept to a minimum.

6.2.2 Constant Displacement Specimens—The CMOD applied to the bolt-load specimen must be known, with an accuracy of $\pm 1\%$ of the indicated reading. Overapplications of displacement of more than 5% and repetitive displacement fluctuations of more than 1% must be avoided during the experiment.

6.3 Displacement Gage—It may be desirable to attach a displacement gage to a constant load specimen to detect crack growth during testing. It is required that a displacement gage be used with the constant displacement specimen to measure the amount of applied displacement (see Section 6.1.3). An electronic CMOD gage can provide a highly sensitive indicator of crack growth for this purpose (see Test Method E 399). However, when placed directly above an environmental chamber containing an aqueous solution for prolonged periods, corrosion may degrade CMOD gages. Also, the CMOD gage should not be allowed to come into direct contact with the solution to avoid possible galvanic action between the gage and the test specimen. A mechanical dial gage placed near the extremity of the moment arm also may be used to detect crack growth.

6.4 Environmental Chamber—It is important that the environmental chamber does not influence the test results either by modifying the environment or the electrochemical potential of the specimen. Influence of the environment chamber or the pressure of the environment should be accounted for in the calibration of the applied K value. The environmental chamber shall enclose the portion of the specimen that contains the crack tip. It shall be configured so that either the test specimen is the only metallic component in contact with the solution or the specimen is electrically isolated from any other metals in contact with the solution. Nonmetallic or corrosion-resistant materials are recommended for the environmental chamber. A sealant might be required between the specimen and the environmental chamber. Sealants selected must not alter the bulk solution chemistry of the test environment. It is recommended that the volume of the environmental chamber be large enough to contain at least 40 ml/cm² of specimen surface area exposed to the solution.⁶

6.5 Potentiostatic Control—Where potentiostatic control of the specimen is desired, an electrochemical cell is required (including an auxiliary electrode such as platinum or graphite, and a reference electrode with specimen potential controlled by a potentiostat). Care must be taken to avoid ground loops and galvanic interference from the clamping and loading fixtures. Oxides on the specimen surface may hamper the achievement of the desired specimen potential. Under some conditions, it may be necessary to mask off a portion of the specimen surface so that proper potentiostatic control can be achieved. It is desirable to include apparatus for measuring and recording electrode potential and applied current (see ASTM Test Method G 5, Standard Reference Method for Making Potentiostatic and Potentiodynamic Anodic Polarization Measurements).

7.0 SPECIMEN CONFIGURATION, SIZE, AND PREPARATION

7.1 Specimen Configuration:

7.1.1 The recommended cantilever beam specimen configuration is shown in Fig. 4. It is recommended that $1 \leq W/B \leq 2$, provided that B , a_0 , and $W - a_0$ meet the validity criteria of Section 7.2. The specimen configuration shown in Fig. 3 does not include side grooves.⁷

7.1.2 The recommended compact specimen configuration is shown in Fig. 5. The configuration does not include side grooves.⁷ For the determination of K_{IEAC} , it is recommended that $1 \leq W/B \leq 2$, provided that B , a_0 , and $W - a_0$ meet the validity criteria of Section 7.2.

⁶The ratio of the specimen free surface area, exposed to the test solution in the chamber, to the crack size affects the anode/cathode area and can affect the corrosion potential in the crack. The area external to the crack should be significantly greater than the crack area.

⁷If crack growth rate information is to be obtained in addition to K_{IEAC} , side grooves may be desirable. Side grooves may promote straight-fronted crack growth with some materials in some environments. Side groove depths with a total thickness reduction of 20% are suggested. Side groove root radii of less than 0.4 mm (0.016 in.) are suggested. Alternative methods to obtain crack growth rate information are available (E 647, ref 22).

Note 2—Caution should be exercised when using side grooves in more aggressive environments.

7.1.3 The recommended bolt-load compact specimen configuration is shown in Fig. 6. The configuration does not include side grooves.⁷ While for the determination of K_{IEAC} it is recommended that W/B is 2:1, a 1:1 ratio can also be used, provided that B , a , and $W - a$ meet the validity criteria of Section 7.2.

7.1.4 Other specimen and loading configurations, for which well-established stress intensity calibrations are available, are acceptable as long as the specimen size requirements of Section 7.2 are met.

7.2 Specimen Size:

7.2.1 For the results to be valid according to this test method, it is required that the specimen be predominantly elastic in its behavior and that one or more of the following criteria be satisfied.

7.2.1.1 For the measurement of K_{IEAC} , it is required that B , a_0 , and $W - a_0$ equal or exceed the quantity $2.5(K_{IEAC}/\sigma_{YS})^2$, where σ_{YS} is the yield strength of the material determined at the temperature of the K_{IEAC} experiment.

7.2.1.2 For the measurement of K_{EAC} , it is required that $W - a_0$ equal or exceed the quantity $(4/\pi)(K_{EAC}/\sigma_{YS})^2$. In this calculation σ_{YS} may be replaced by σ_Y for high-work hardening materials with an ultimate to yield strength ratio greater than 1.3. These requirements are consistent with those used in Test Method E 647.

7.2.1.3 For the cantilever beam and compact specimens, it is recommended that the crack length (total length of the machined notch plus the fatigue precrack) be between 0.45 and 0.55 W whenever possible. However, normalized crack length values, a/W , may range from 0.25 to 0.75 in extreme instances, provided the requirements of Section 9.3 are met.

7.2.1.4 For the bolt-load compact specimen, applied K values continuously decrease with increasing crack length, so that large crack lengths can be used. It is recommended that the total crack length (total length of the machined notch plus the fatigue precrack and the crack growth) be between 0.30 and 0.95 W , provided the requirements of Section 8.8.2.5 are met.

7.3 Specimen Preparation:

7.3.1 The dimensional tolerances and surface finishes shown in Figs. 4 through 7 shall be followed in the specimen preparation.

7.3.2 Care should be taken in machining to prevent contamination of specimen and notch surfaces that are difficult or impossible to clean. An example of this is the copper deposit left by electric discharge machining (EDM) with a copper electrode.

7.3.3 Prior to fatigue precracking and testing, specimens should be cleaned in accordance with Standard Practice G 1.

7.3.4 It is required that the specimen be fatigue precracked before testing. Fatigue precracking may be conducted in an ambient-air environment. The single-edge notched specimen may be fatigue precracked either in cantilever bending or in three-point bending. Fatigue precracking should be performed with the specimen fully heat treated to the condition in which it is to be tested.

7.3.4.1 The fatigue precrack shall extend to a depth of not less than $0.10 B$ or 1.0 mm (0.04 in.), whichever is greater, beyond the tip of the machined notch as measured on each face of the specimen. It is required that the final 1-mm (0.04-in.) increment of fatigue precracking be conducted at a maximum stress intensity factor (K_{max}) of not more than 80% of the expected K_{EAC} value. The plane of the crack shall be parallel to both the specimen width and thickness directions within $\pm 10^\circ$.

7.3.4.2 Note that in some materials highly sensitive to stress corrosion cracking (such as ultrahigh-strength alloys), K_{EAC} values can be very low (less than $20 \text{ MPa}/\sqrt{\text{m}}$). Thus, permissible K_{max} levels for precracking highly sensitive materials might be restricted to small values. This restriction could dictate lengthy periods of fatigue precracking. Under these circumstances, it may be necessary to initiate fatigue precracking at K_{max} levels higher than 60% of K_{EAC} and to follow a load-shedding (K -decreasing) program in fatigue cracking, as described in Test Method E 647. Load-shedding procedures provide an alternative means of achieving the final critical increment of precracking at adequately low K_{max} (no more than 60% of K_{EAC}).

7.3.5 Care should be taken to prevent the contamination of the crack after precracking and before testing.

8.0 GENERAL PROCEDURE

8.1 Number of Tests—It is difficult to prescribe in advance the number of tests required to establish a valid K_{EAC} or K_{IEAC} value by this method. The K_{EAC} or K_{IEAC} value is determined from several experiments at K levels in which specimens failed after a relatively long time under load or did not fail within a prescribed period (discussed in Section 8.4). For the cantilever beam and compact specimens, in order to meet the load-bracketing requirements of Section 8.5, it is suggested that at least four K levels, and perhaps up to six, be investigated to ensure a measurement of K_{EAC} or K_{IEAC} . For the bolt-load compact specimen, it is suggested that at least two, and perhaps up to four, specimens be tested to ensure a measurement of K_{EAC} or K_{IEAC} . As a general practice, it is recommended that test data be displayed graphically in terms of initial applied K (K based upon the applied load or displacement and a_0) versus logarithmic time to failure. Guidance for the estimation of K_{EAC} or K_{IEAC} can be obtained for steels, aluminum alloys, and titanium alloys from References 14 through 17. If neither past experience nor these references are helpful in making this estimate, a screening program with a limited number of specimens may be needed as a first phase in the testing program.

8.2 Exposure to the Environment—With some environment-material combinations, preconditioning of the specimen in the environment prior to load or displacement application will greatly influence the resulting K_{EAC} or K_{IEAC} values. When this is the case the specimen shall be exposed to the environment immediately preceding the test for at least 10% of the total test time, or eight hours, whichever is less. The specimen may be loaded after this pre-exposure, either incrementally or continuously; however, the rate of loading should not exceed $100 \text{ MPa}/\sqrt{\text{m}}$ per minute.

8.3 Load or Displacement Changes—Any significant change or interruption in loading, displacement, temperature, environmental exposure, or applied potential (if appropriate) needs to be evaluated and may invalidate the measurement of K_{EAC} or K_{IEAC} . Such interruptions need to be reported with the results. Occasional interruption of the load usually does not influence the results but overloads of more than 5% and repetitive load fluctuations of more than 1% must be avoided and would invalidate the results.

8.4 Test Duration—A test will continue until one of the following occurs: (1) fracture, (2) evidence of subcritical crack growth is observed in the specimen, (3) a pre-established period of time has elapsed. Determining an adequate, but not excessive, test duration for threshold measurement is one of the most difficult aspects of K_{EAC} testing (ref 5). The test duration that is adequate for a valid threshold measurement depends strongly on the material and the environment. For constant load tests involving ambient-temperature solutions of sodium chloride, including natural and ASTM substitute seawater (see Specification D 1141), the guideline test durations listed below are considered long enough to ensure that a valid threshold has been measured, but the actual times could be much shorter and need to be determined empirically. For constant displacement tests with relatively non-aggressive environments, the guideline test durations listed below may not be long enough to ensure that a valid threshold has been measured. The actual times could be longer and need to be determined empirically by using one or more trial samples. From this result the test duration can be more accurately determined for the remainder of the tests.

steels ($\sigma_{YS} < 1,200$ MPa)	10,000 hours
steels ($\sigma_{YS} > 1,200$ MPa)	5,000 hours
aluminum alloys	10,000 hours
titanium alloys	1,000 hours

The large differences in guideline test durations among various alloys reflect inherent differences in incubation periods and in crack growth kinetics. In some instances, it may be impractical or impossible to achieve test durations as long as these. Under such circumstances, all data used in a K_{EAC} or K_{IEAC} determination should be qualified as to test duration (see Section 10.1.8). Adequate test durations could be much shorter in environments that are more aggressive than sodium chloride solutions, such as aqueous solutions of hydrogen sulfide, caustics, or ammonia.

8.5 Load Bracketing—The interval in applied K levels between specimens depends on the desired accuracy of the K_{EAC} or K_{IEAC} value and the number of specimens to be tested. The interval should be in the range of 10 to 20% of the estimated K_{EAC} or K_{IEAC} value.

8.6 Environmental Monitoring or Control—Environmental parameters are of vital importance in K_{EAC} or K_{IEAC} testing; therefore, careful monitoring and control of the solution is required. Temperature, pH, conductivity, dissolved oxygen content, and electrode potential are variables that can affect environment-assisted cracking processes. Among these parameters, it is important to note that the electrode potential can exert a very strong influence on K_{EAC} or K_{IEAC} . It is especially important that this parameter be carefully monitored and/or controlled either continuously or at regular intervals throughout the test. Every chamber opening, specimen inspection, and environment refreshing may result in a swing of the potential.

8.6.1 It is necessary to maintain enough solution in the environmental chamber to ensure that the crack-tip region of the specimen is immersed in the corrosive environment at all times and to ensure that the concentration of the electrolyte is not increased by evaporation. Long-term testing is conducive to the development of leaks at sites of contact between the environmental chamber and the specimen; thus, seals between the chamber and the specimen should be inspected regularly for leakage.

8.6.2 For tests involving sodium chloride solutions, replace the test solution at least weekly. It may be desirable to provide a circulation system to ensure a constant level of aeration of the bulk solution. The effects, if any, of aeration on K_{EAC} measurements are complex and not completely understood. Theoretical modeling studies have indicated, at least in steels, that the crack-tip region is completely deoxygenated regardless of the dissolved oxygen concentration in the bulk solution (ref 18). In addition, the CO_2 from the air may play an important role. Laboratory studies on steels have supported this hypothesis by demonstrating a lack of response to changes in bulk solution dissolved oxygen content in K_{EAC} tests on a steel in a sodium chloride solution (ref 19). However, this may not be the case for titanium alloys, where deaeration has been demonstrated to have an effect on K_{EAC} values. Also, note that aeration increases dissolved oxygen and, thus, may lower the pH, raise the corrosivity of the solution, and make the free corrosion potential more anodic. For some solutions, oxygen gradients along the crack length can establish potential gradients which assist ion migration into or out of the crack thus influencing the K_{EAC} measurement.

8.6.3 For tests in solutions other than sodium chloride, care should be taken to refresh the solution at regular intervals, if required, to maintain the desired environmental conditions. The frequency of refreshment required will depend on many variables and should be determined for the particular environment/test material combination being studied.

8.6.4 For tests that require polarizing the specimen to a potential other than the free corrosion potential (Test Method G 5), several recommendations are offered. The use of a potentiostat is recommended rather than coupling the specimen to a dissimilar metal. However, when a potentiostat is used, appropriate care must be given to specimen grounding. For tests involving cathodic polarization with sacrificial anodes, periodic cleaning of the anodes and the specimen may be necessary if significant corrosion or calcareous deposits are observed. It is further recommended that, when using sacrificial anodes, the surface area of the anode should be no less than 25% of the specimen surface in contact with the solution. It is essential that the anodes be located so that the specimen is polarized uniformly throughout the test area. In this regard, adequate spacing between the specimen and anodes is necessary. Cathodic or anodic polarization of the sample may promote changes in the solution chemistry particularly the solution pH. As a result, when polarizing currents are applied, the pH should be checked more frequently and precautions not required for open circuit potential experiment should be considered.

8.6.5 For bolt-load compact tests, remove the bolt-load at the end of the test while measuring the CMOD. The change in CMOD upon unloading may be less than that of the original bolt-loading of the specimen, because of the presence of corrosion products on the crack surfaces or load relaxation. If the change in CMOD upon unloading is less than 90% of that of the loading, check for presence of corrosion products and for evidence of load relaxation (see Section 5.1.7). If no reason can be found for a change in CMOD due to unloading that is less than 90% of that due to loading, then the constant displacement test method may not be suitable for these test conditions, and a constant load test should be considered.

8.7 Post-Test Examination—Specimen fracture surfaces must be visually examined after testing. The fracture surfaces of specimens that did not fail shall be examined for evidence of environment-assisted crack growth. Evidence of crack growth is taken as proof that the specimen was loaded at a K level higher than K_{EAC} or K_{IEAC} .

8.7.1 Break the specimen to expose the crack, taking care to minimize deformation. Cooling ferritic steel specimens enough to ensure brittle behavior may be helpful. Advancing the crack by fatigue may be needed in more ductile materials.

8.7.2 Inspect the tip of the initial fatigue precrack, looking for evidence of crack extension. Characterize the fracture surface of the crack extension, in comparison with the fracture surface formed by breaking the specimen to expose the crack. This inspection must be made with an instrument capable of resolving 0.025 mm (0.001 in.). A scanning electron microscope is useful for the fracture surface inspection and characterization.

8.8 Specimen Measurement—Specimen dimensions shall conform to the dimensions and tolerances shown in Figs. 3 through 6. Three fundamental measurements are necessary to calculate K , namely: thickness, B ; original crack size, a_o ; and width, W . If significant metal loss is expected during the experiment, dimensions B and W must be measured prior to testing.

8.8.1 Measure the thickness, B , to the nearest 0.025 mm (0.001 in.) or to 0.1%, whichever is larger, at no fewer than three equally spaced positions along the line of expected crack extension from the fatigue crack tip to the unnotched side of the specimen. Record the average of the three measurements as B .

8.8.2 Measure the original crack size, a_o , after fracture to the nearest 0.5% at the following three positions: at the center of the crack front, and midway between the center of the crack front and the ends of the crack front on each side surface. Calculate the average of the three measurements and use the resulting crack length to calculate K . The following requirements apply to the fatigue crack front:

8.8.2.1 The difference between any two of the three crack length measurements shall not exceed 10% of the average.

8.8.2.2 No part of the crack front shall be closer to the machined starter notch than 0.10 B or 1 mm (0.04 in.) minimum.

8.8.2.3 The surface crack length measurements shall not differ from the average crack length by more than 15%.

8.8.2.4 The difference between these two surface measurements shall not exceed 10% of the average crack length.

8.8.2.5 For the bolt-load compact specimen, the surface remaining ligament measurements (that is, $W - a$) shall not differ from the average remaining ligament measurement by more than 15%.

8.8.3 Measure the width, W , using the designations in Figs. 3 through 5 appropriate to the specific specimen geometry.

8.8.4 The plane of the original crack shall be parallel to both the specimen width and thickness directions within $\pm 10^\circ$.

9.0 CALCULATIONS AND INTERPRETING RESULTS

9.1 Determining the Stress Intensity Factor, K :

9.1.1 The formula for the cantilever beam specimen, taken from Reference 20, is:

$$K_I = \frac{M}{B(W)^{\frac{3}{2}}} f(a_o/W)$$

where:

$$f(a_o/W) = \frac{6(a_o/W)^{1/2}}{\alpha^{3/2}} \{1.9878 - 1.3253 (a_o/W) + (\alpha)(a_o/W) [-3.8308 + 10.1081(a_o/W) - 17.9415(a_o/W)^2 + 16.8282(a_o/W)^3 - 6.2241(a_o/W)^4]\}$$

where:

α = $1 - (a_o/W)$ and
 M = bending moment on the crack plane

where:

M = $W_a L_a + W_t L$
 W_a = weight of arm
 L_a = distance from notch plane to center of gravity of arm
 W_t = total weight of platen, platen support, and added weight
 L = moment arm as shown in Fig. 1

where:

B = specimen thickness⁸ as determined in Section 8.8.1
 W = specimen width as determined in Section 8.8.3
 a_o = original crack size as determined in Section 8.8.2

This expression for K is valid for $0 < a/W < 1$.

⁸For side grooved specimens replace B with $B_{effective}$ where $B_{effective} = \sqrt{BB_N}$ and B_N is the net thickness.

9.1.2 The stress intensity factor formula for the compact specimen, taken from Test Method E 399, is:

$$K = \left[\frac{P}{BW^{\frac{3}{2}}} \right] f\left(\frac{a_0}{W}\right)$$

where:

$$f\left(\frac{a_0}{W}\right) = \frac{\left(2 + \frac{a_0}{W}\right)}{\left(1 - \frac{a_0}{W}\right)^{\frac{3}{2}}} \left[0.886 + 4.64\left(\frac{a_0}{W}\right) - 13.32\left(\frac{a_0}{W}\right)^2 + 14.72\left(\frac{a_0}{W}\right)^3 - 5.6\left(\frac{a_0}{W}\right)^4 \right]$$

and:

- a_0 = original crack size as determined in Section 8.8.2
- B = specimen thickness⁸ as determined in Section 8.8.1
- W = specimen width as determined in Section 8.8.3
- P = load

This expression for K is valid for a/W from 0.2 to 1.

9.1.3 The stress intensity factor formula for the bolt-load compact specimen, taken from Reference 21, is:

$$K_I = [V_m E / W^{1/2}] f(a/W)$$

$$f(a/W) = [1 - a/W]^{1/2} [0.654 - 1.88(a/W) + 2.66(a/W)^2 - 1.233(a/W)^3]$$

where:

- V_m = crack-mouth opening displacement on the specimen face as determined in Section 6.3
- E = Young's modulus
- a = original or final crack size as determined in Sections 8.8.2 and 8.8.4
- B = specimen thickness⁸ as determined in Section 8.8.1
- W = specimen width as determined in Section 8.8.3

This expression for K is valid for $H/W = 0.486$ and for a/W from 0.3 to 1.

⁸For side grooved specimens replace B with $B_{\text{effective}}$ where $B_{\text{effective}} = \sqrt{BB_N}$, and B_N is the net thickness.

9.2 Determining K_{EAC} or K_{IEAC} :

9.2.1 For the cantilever beam and compact specimens, the value of K_{EAC} or K_{IEAC} determined by this method is the highest applied K level that did not cause a fracture or evidence of subcritical crack growth in a specimen after reaching the recommended test duration (determined by the procedure described in Section 8.7).

9.2.2 For the bolt-load compact specimen, the value of K_{EAC} or K_{IEAC} determined by this method is the lowest applied K level that shows evidence of subcritical crack growth in a specimen after reaching the recommended test duration (determined by the procedure described in Section 8.7).

9.3 Validity Check:

9.3.1 Calculate the value of the parameter $2.5(K_{IEAC}/\sigma_{YS})^2$, where σ_{YS} is the 0.2% offset tensile yield strength at the same temperature as the threshold K test (see Test Method E 8). This quantity must be less than each of B , a_0 , and $W - a_0$ to meet the primary plane strain validity criteria for K_{IEAC} .

9.3.2 Calculate the value of the parameter $(4/\pi)(K_{EAC}/\sigma_{YS})^2$; in this calculation, σ_{YS} may be replaced by σ_y for high work-hardening materials with an ultimate to yield strength ratio greater than 1.3. This quantity must be less than $(W - a_0)$ to meet the validity criteria for K_{EAC} .

10.0 REPORT

10.1 The report shall include the following information for each specimen tested.

10.1.1 The type of specimen tested and the principal dimensions of the specimen, including thickness, width, notch depth, precrack length, crack plane orientation as defined in Test Method E 399 and, if present, dimensions of side-groove.

10.1.2 Descriptions of the test equipment, including loading fixture, method of loading, rate of initial loading, displacement gages, environmental chamber, and all equipment used for environmental monitoring and control.

10.1.3 Description of the tested material, including available chemical analyses, processing, and mechanical property data.

10.1.4 Details of the fatigue precracking procedure, including the value of K_{max} and the stress intensity range, ΔK used in the final increment precracking (defined in Section 7.3.4).

10.1.5 Composition of the bulk solution, time in solution before loading, temperature, and frequency of replacement of the bulk solution throughout the duration of the test.

10.1.6 Results of monitoring or control of environmental variables, including specimen potential and temperature, pH, and dissolved oxygen content of the bulk solution. Such variables must be reported in terms of both the normal daily range experienced throughout the duration of the test and relevant trends.

10.1.7 Fracture appearance, including fatigue crack irregularity, out-of-plane cracking, crack branching, shear lips, and evidence of subcritical crack growth in specimens.

10.1.8 K_{IEAC} and K_{EAC} qualified relative to the following:

10.1.8.1 K_I and time-to-failure values bracketed in the determination of threshold.

10.1.8.2 Number of replicate tests included in the bracketing.

10.1.8.3 Duration of all tests that did not result in failure (run outs).

10.1.8.4 The a_0/W values of the specimens used in threshold determination.

10.1.8.5 Whether the validity criteria for specimen dimensions were met in each instance.

10.1.9 Anomalies, interruptions, or transients encountered during the test must be described in terms to magnitude, time of occurrence, and duration.

11.0 PRECISION AND BIAS

11.1 Precision:

11.1.1 The precision of K_{EAC} or K_{IEAC} determinations is a function of the precision of the several specimen dimensions and test stand measurements, the precision of the load measurement, and the precision of the post-test measurement of crack length. In addition, significant variations in the K_{EAC} or K_{IEAC} value can result if the active environmental parameters are not adequately controlled and if the tested material is not homogeneous. It is not possible to assess the precision of the test in the face of so many variables. However, it is possible to derive useful information concerning the precision of a K_{EAC} or K_{IEAC} measurement from the results of two interlaboratory test programs (refs 22,23). In these programs it was attempted to choose a homogeneous test material and the test environment was chosen as one that was easy to achieve.

11.1.2 Reference 22 reported results of an interlaboratory test program conducted by an ASTM Joint Task Group E24.04.02/G01.06.04. The program involved testing precracked cantilever-beam specimens of AISI 4340 steel, heat treated to a yield strength of 1240 MPa in 3.5% NaCl aqueous solution at room temperature and at the freely corroding potential. Based on results provided by eight laboratories, the apparent K_{IEAC} after 1000 hours of testing was determined to have a mean value of 34.5 MPa√m with an estimated 95% confidence interval of 5.8 MPa√m. One of the participating laboratories extended the testing time to 20,000 hours and measured a K_{IEAC} value of 30 MPa√m. This value is consistent with those measured in the 4000-hour experiments.

11.1.3 Reference 23 reported results of an interlaboratory test program conducted by the 129th Committee of the Japan Society for the Promotion of Science. The test program was quite similar to Reference 21 with regard to specimens, materials, and environment, except that longer tests were conducted. In one test material, based on results provided by five laboratories, the apparent K_{IEAC} after 4000 hours of testing was determined to have a mean value of 44.3 MPa√m with a standard deviation of 4.33 MPa√m. In a second test material, based upon 4000-hour tests

conducted by six laboratories, the apparent K_{IEAC} had a mean value of 28.9 MPa $\sqrt{m}$ with a standard deviation of 5.52 MPa $\sqrt{m}$.

11.1.4 Variations similar to those reported in References 22 and 23 should be expected from future experiments.

11.2 Bias—There is no accepted standard value of K_{IEAC} for any material. In the absence of a fundamental value, no meaningful statement can be made concerning the bias of data.


12.0 KEYWORDS

12.1 constant load; environment-assisted cracking; metallic materials; plane strain; precracked specimen; threshold stress intensity factor

REFERENCES


- (1) Gangloff, R.P., and Ives, M.B., Eds., *Environment-Induced Cracking of Metals*, NACE, Houston, TX, 1990.
- (2) Brown, B.F., "A New Stress-Corrosion Test for High-Strength Alloys," *Materials Research and Standards*, Vol. 6, No. 3, March 1966, pp. 129-133.
- (3) Brown, B.F., "On the Existence of a Threshold Stress for Corrosion Cracking in Titanium Alloys in Salt Water," *Journal of Materials*, JMLSA, Vol. 5, No. 4, December 1970, pp. 786-791.
- (4) Oriani, R.A., and Josephic, P.H., "Equilibrium Aspects of Hydrogen Induced Cracking of Steels," *Acta Metallurgica*, Vol. 22, 1974, pp. 1065-1074.
- (5) *Characterization of Environmentally Assisted Cracking for Design; State of the Art*, NMAP-386. National Materials Advisory Board, National Academy Press, Washington, DC, 1982.
- (6) Fessler, R.R., and Barlo, T.J., "Threshold-Stress Determination Using Tapered Specimens and Cyclic Stresses," *ASTM STP 821*, 1984, pp. 368-382.
- (7) Crooker, T.W., Hauser, J.A., II, and Bayles, R.A., "Ripple-Loading Effects on Stress-Corrosion Cracking in Steels," *Proceedings of the Third International Conference on Environmental Degradation of Engineering Materials*, Pennsylvania State University, April 13-15, 1987, pp. 521-532.
- (8) Fujii, C.T., "Effect of Specimen Dimensions on K_{ISCC} Determination by the Cantilever Method," *NRL Report 8236*, Naval Research Laboratory, Washington, DC, May 31, 1978.
- (9) Kobayashi, J.I., and Takeshi, Y., "Evaluation of Resistance of Steel Plate to Sulfide Stress Cracking in Sour West Service," *Predictive Capabilities in Environmentally Assisted Cracking*, PVP-Vol. 99, American Society of Mechanical Engineers, 1985, pp. 223-234.
- (10) Piper, D.E., Smith, S.H., and Carter, R.V., "Corrosion Fatigue and Stress-Corrosion Cracking in Aqueous Environments," *Metals Engineering Quarterly*, Vol. 8, No. 3, 1968, pp. 50-63.
- (11) Ciaraldi, S.W., "Application of a Double Cantilever Beam Specimen to Stress-Corrosion Evaluation of High-Alloy Production Tubulars," *Corrosion 83, Paper No. 162*, NACE, Houston, TX, 1983.
- (12) Ritter, J.C., "Modified Thickness Criterion for Fracture Toughness Testing," *Engineering Fracture Mechanics*, Vol. 9, 1977, pp. 529-540.

- (13) Novak, S.R., "Effect of Prior Uniform Plastic Strain on the K_{Isc} of High Strength Steels in Sea Water," *Engineering Fracture Mechanics*, Vol. 5, 1973, pp. 727-763.
- (14) Gangloff, R.P., "A Review and Analysis of the Threshold for Hydrogen Environment Embrittlement of Steels," *Corrosion Prevention and Control*, 33rd Sagamore Army Materials Research Conference, Levy, M., and Isserow, S., Eds., U.S. Army Laboratory Command, Watertown, MA, 1986, pp. 64-111.
- (15) Hertzberg, R.W., *Deformation and Fracture Mechanics of Engineering Materials*, Ch. 11, 2nd Ed., John Wiley and Sons, New York, NY, 1983.
- (16) *Atlas of Stress-Corrosion and Corrosion Fatigue Curves*, McEvily, A.J., Ed., ASM International, Metals Park, OH, 1990.
- (17) Crykalis, W.F., *Environment-Sensitive Fracture on Engineering Materials*, Forplis, Z.A., Ed., TMS-AIME, Warrendale, PA, 1979, pp. 303-313.
- (18) Gangloff, R.P., and Turnbull, A., "Crack Electrochemistry Modeling and Fracture Mechanics Measurement of the Hydrogen Embrittlement Threshold in Steel," *Modeling Environmental Effects on Crack Initiation and Propagation*, TMS-AIME, Warrendale, PA, 1986, pp. 55-81.
- (19) Judy, R.W., Jr., King, W.E., Jr., Hauser, J.A., II, and Crooker, T.W., "Influence of Experimental Variables on da/dt and K_{Isc} Measurement in High-Strength Steels," *ASTM STP 1049*, 1990, pp. 410-422.
- (20) Baratta, F.I., "Stress-Intensity Factor Solution for Cantilever Loaded-Beam Specimen," 1992 letter, on file at ASTM.
- (21) Underwood, J.H., Olmstead, V.J., Askew, J.C., Kapusta, A.A., and Young, G.A., "Environmentally Controlled Fracture of an Overstrained A723 Steel Thick-Wall Cylinder," *ASTM STP 1189*, 1993, pp. 443-460.
- (22) Wei, R.P., and Novak, S.R., "Interlaboratory Evaluation of K_{Isc} and da/dt Measurement Procedures for High-Strength Steels," *Journal of Testing and Evaluation*, Vol. 15, 1987, pp. 38-75.
- (23) Yokobori, T., Watanabe, J., and Iwadata, T., "Evaluation of the K_{Isc} Testing Procedure by Round Robin Tests on Steels," *ASTM STP 945*, 1985, pp. 843-866.

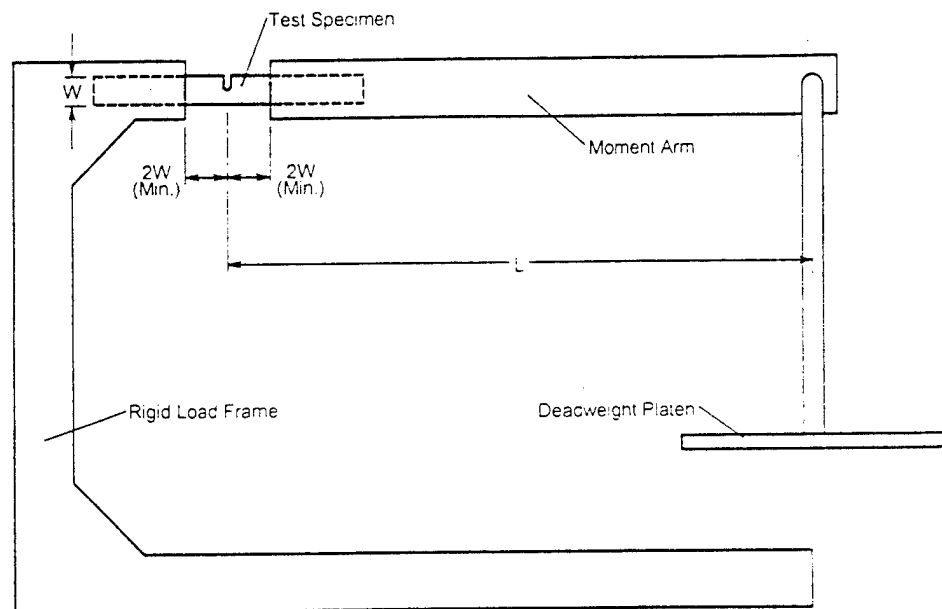

NOTE—The length of the moment arm (L) should be equal to or greater than $8W$.

FIG. 1 Typical Configuration of a Dead-Weight Cantilever-Beam Loading Fixture

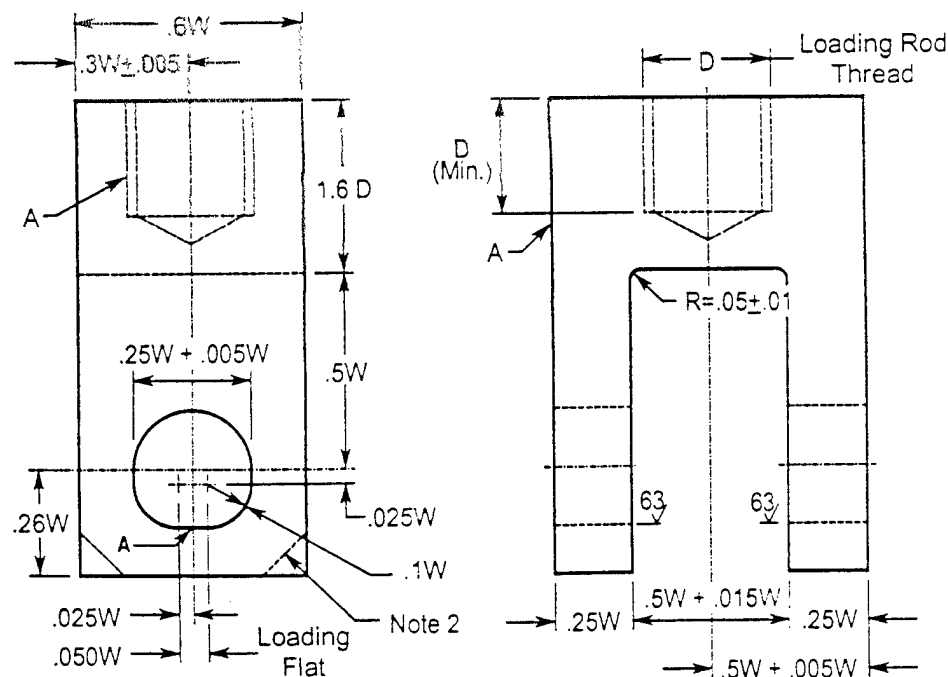

NOTE 1—Surfaces designated as "A" must be flat in-line, and perpendicular as applicable to within 0.051 mm TIR.

NOTE 2—Pin diameter = $0.24W (+0.000W/-0.005W)$. For specimens "A" with $\sigma_{ys} > 1379$ MPa the holes in the specimen and in the clevis may be $0.3W (+0.005W/-0.000W)$ and the pin diameter = $0.268W (+0.000W/-0.005W)$.

NOTE 3—Corners of the clevis may be removed if necessary to accommodate a clip gage.

FIG. 2 Tension Test Clevis Design

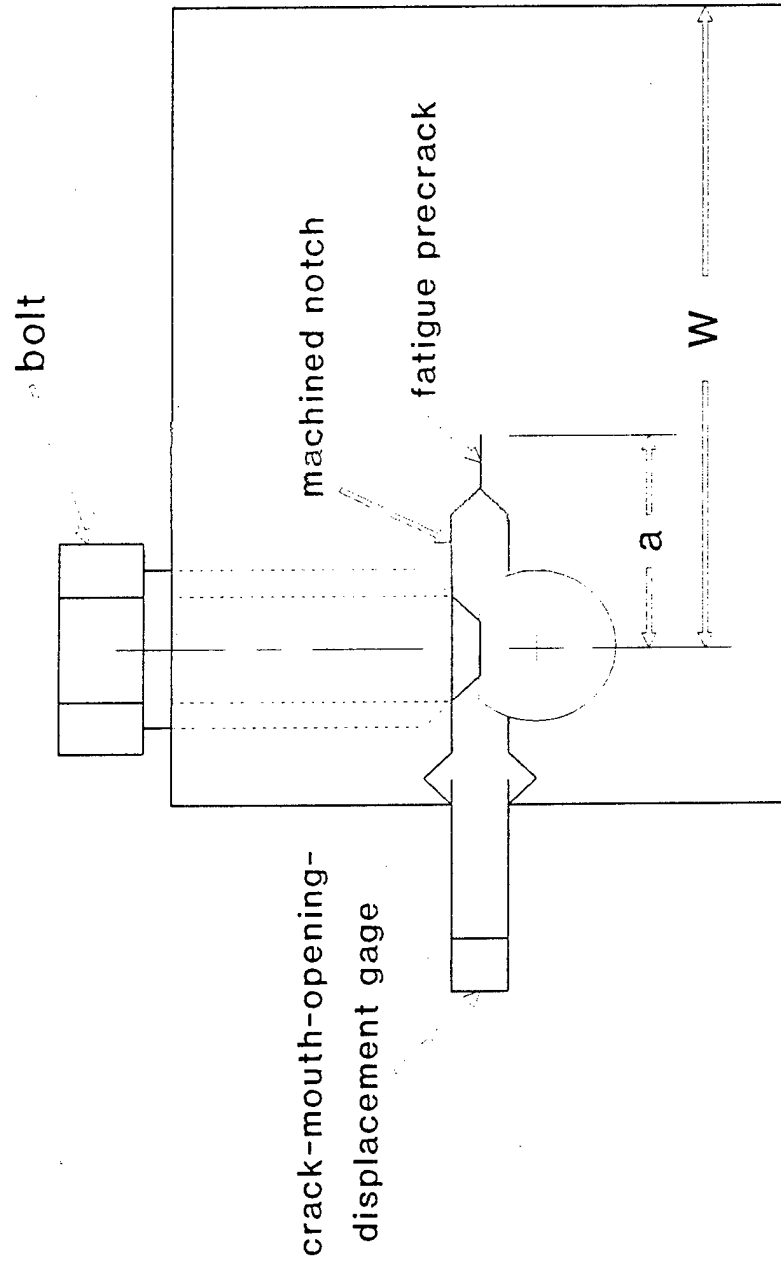


Fig. 3 Typical Test Arrangement for Constant Displacement $K_{I, EAC}$ Tests
with Modified Bolt-Load Compact Specimen; $H/W = 0.486$

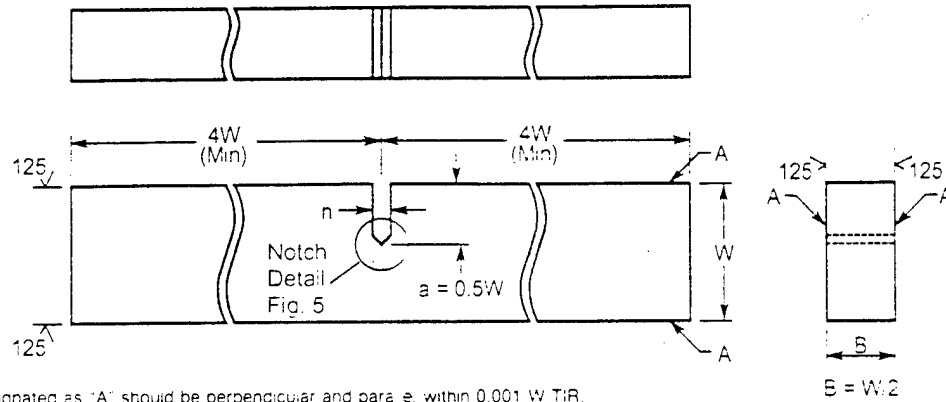


FIG. 4 Beam Specimen

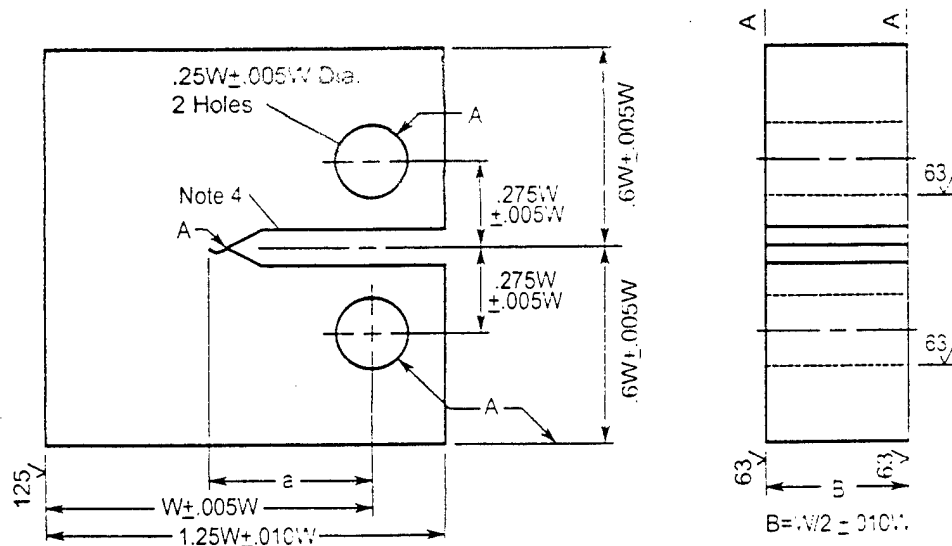


FIG. 5 Standard Proportions and Tolerances for the Compact Specimen



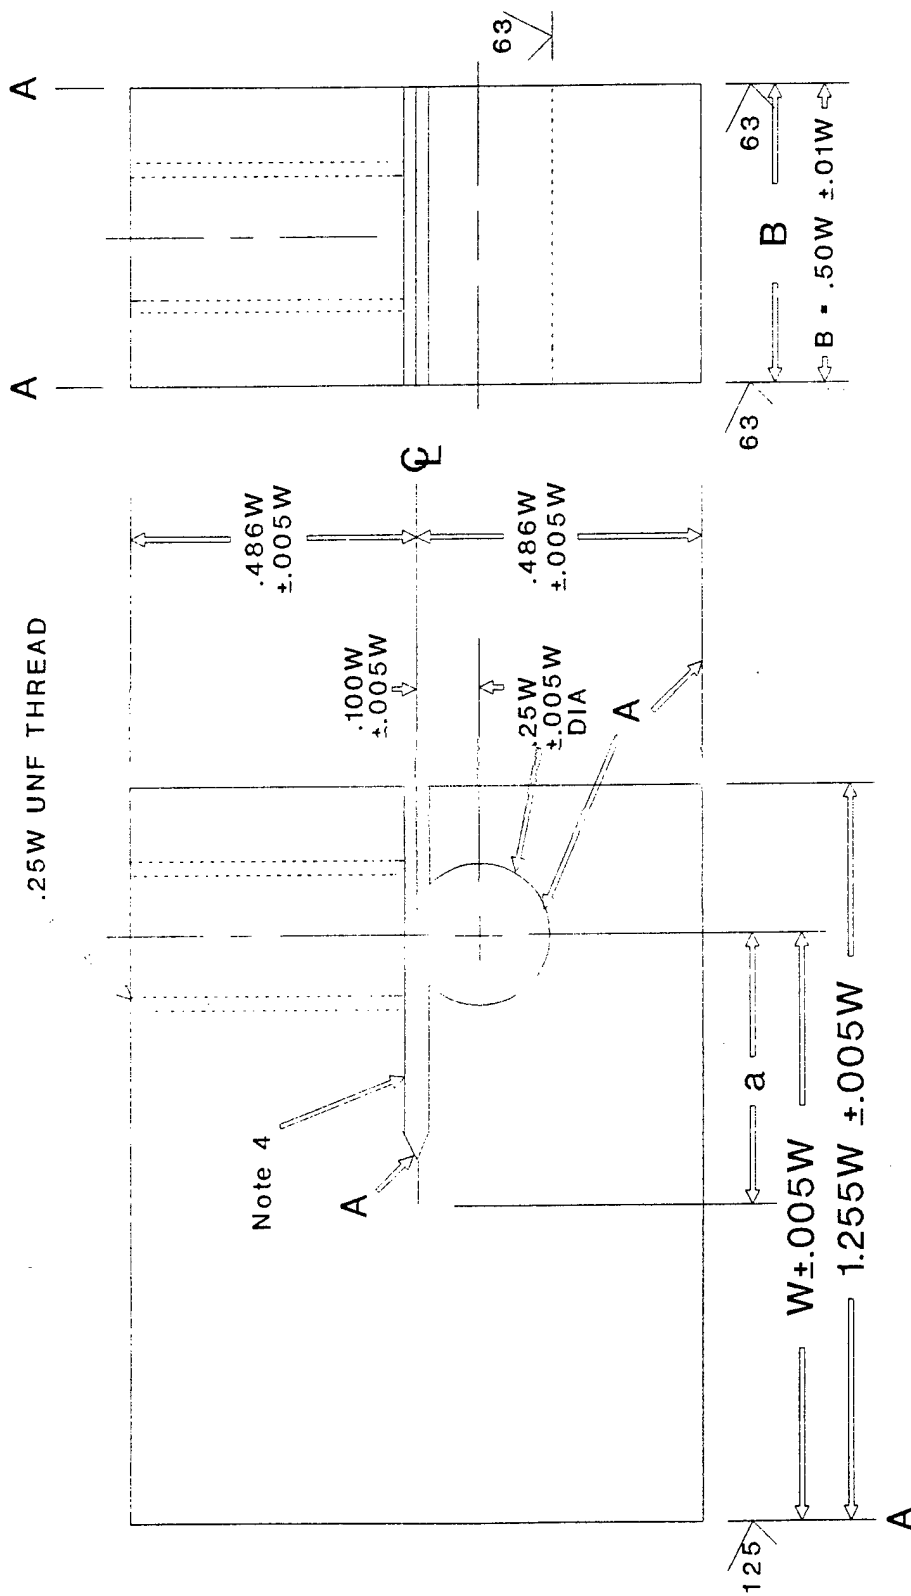


Fig. 6 Standard Configuration for the Modified Bolt-Load Compact Specimen; $H/W = 0.486$

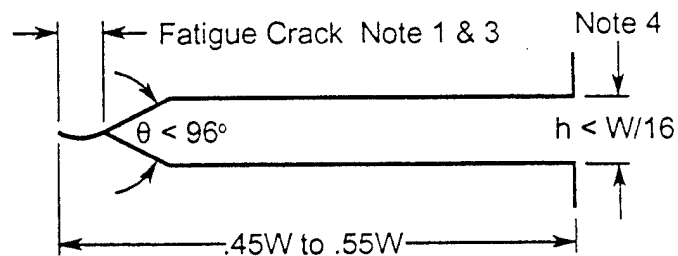

Straight Through Notch

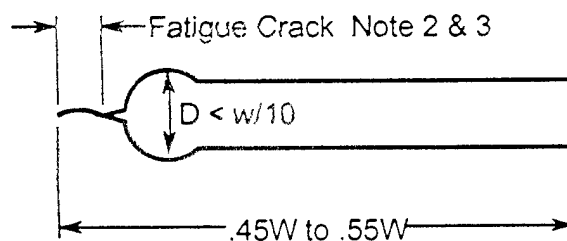

Slot Ending in Drilled Hole

- NOTE 1—Fatigue crack extension on each surface of the specimen.
 NOTE 2—Fatigue crack extension on each surface of the specimen from the stress riser tipping the hole shall be at least 0.5 D or 1.3 mm whichever is larger.
 NOTE 3—Crack starter notch shall be perpendicular to the specimen surface and to the intended direction of crack propagation within $\pm 2^\circ$
 NOTE 4—Notch width h need not be less than 1.6 mm

FIG. 7 Crack Starter Notch and Fatigue Crack Configurations

DISCUSSION AND CLOSING

The important technical additions to ASTM Method E1681 in the proposed modifications given above are:

- Specimen configuration shown in Figures 3 and 6
- Expressions for stress intensity factor given in Section 9.1.3
- Discussion of load relaxation that can occur with the bolt-load specimen, given in Sections 5.1.7 and 8.6.5

The specimen configuration is the same as that used in the original work by Wei and Novak (ref 2); it has worked well for a wide variety of materials, so there is no reason to change. The K expressions are from prior Army results (ref 1). They agree closely with other expressions in the literature, but have a simpler form and can be used over a broader range of crack depths. The load relaxation discussions warn the user of the standard about drops in load that can occur, particularly when testing materials of significantly lower strength than the 1100 to 1200 MPa yield strength steels of the Army applications discussed here.

The proposed modifications to ASTM Standard E1681 described here were developed in close association with investigations of environmental cracking in cannon components, so they have direct application to the Army. Technical input from universities, industry, and other government organizations during the recently completed ASTM Committee ballot has shown that there is broadly based interest in and application for the modified standard. The final ASTM-wide ballot that is now underway will complete the development of the modified standard.

REFERENCES

1. Underwood, J.H., Olmstead, V.J., Askew, J.C., Kapusta, A.A., and Young, G.A., "Environmentally Controlled Fracture of an Overstrained A723 Steel Thick-Wall Cylinder," *Fracture Mechanics: Twenty-Third Symposium, ASTM STP 1189*, (Ravinder Chona, Ed.), American Society for Testing and Materials, Philadelphia, 1993, pp. 443-460.
2. Wei, R.P., and Novak, S.R., "Interlaboratory Evaluation of K_{Isc} and da/dt Determination Procedures for High Strength Steels," *Journal of Testing and Evaluation*, Vol. 15, No. 1, Jan. 1987, pp. 38-75.
3. ASTM Standard E1681, "Test Method for Determining a Threshold Stress Intensity Factor for Environment-Assisted Cracking of Metallic Materials Under Constant Load," *1996 Annual Book of Standards, Volume 03.01*, American Society for Testing and Materials, West Conshohocken, PA, 1997, pp. 980-989.
4. Troiano, E., Underwood, J.H., Scalise, A., O'Hara, G.P., and Crayon, D., "Fatigue Analysis of a Vessel Experiencing Pressure Oscillations," *Fatigue and Fracture Mechanics: 28th Volume, ASTM STP 1321*, (J.H. Underwood, B.D. MacDonald, M.R. Mitchell, Eds.), American Society for Testing and Materials, West Conshohocken, PA, 1997, to be published.
5. Vigilante, G.N., Underwood, J.H., Crayon, D., Tauscher, S., Sage, T., and Troiano, E., "Hydrogen-Induced Cracking Tests of High-Strength Steels and Nickel-Iron Base Alloys Using the Bolt-Loaded Specimen," *Fatigue and Fracture Mechanics: 28th Volume, ASTM STP 1321*, (J.H. Underwood, B.D. MacDonald, M.R. Mitchell, Eds.), American Society for Testing and Materials, West Conshohocken, PA, 1997, to be published.

TECHNICAL REPORT INTERNAL DISTRIBUTION LIST

	<u>NO. OF COPIES</u>
CHIEF, DEVELOPMENT ENGINEERING DIVISION	
ATTN: AMSTA-AR-CCB-DA	1
-DB	1
-DC	1
-DD	1
-DE	1
CHIEF, ENGINEERING DIVISION	
ATTN: AMSTA-AR-CCB-E	1
-EA	1
-EB	1
-EC	1
CHIEF, TECHNOLOGY DIVISION	
ATTN: AMSTA-AR-CCB-T	2
-TA	1
-TB	1
-TC	1
TECHNICAL LIBRARY	
ATTN: AMSTA-AR-CCB-O	5
TECHNICAL PUBLICATIONS & EDITING SECTION	
ATTN: AMSTA-AR-CCB-O	3
OPERATIONS DIRECTORATE	
ATTN: SIOWV-ODP-P	1
DIRECTOR, PROCUREMENT & CONTRACTING DIRECTORATE	
ATTN: SIOWV-PP	1
DIRECTOR, PRODUCT ASSURANCE & TEST DIRECTORATE	
ATTN: SIOWV-QA	1

NOTE: PLEASE NOTIFY DIRECTOR, BENÉT LABORATORIES, ATTN: AMSTA-AR-CCB-O OF ADDRESS CHANGES.

TECHNICAL REPORT EXTERNAL DISTRIBUTION LIST

	<u>NO. OF COPIES</u>		<u>NO. OF COPIES</u>
ASST SEC OF THE ARMY RESEARCH AND DEVELOPMENT ATTN: DEPT FOR SCI AND TECH THE PENTAGON WASHINGTON, D.C. 20310-0103	1	COMMANDER ROCK ISLAND ARSENAL ATTN: SMCRI-SEM ROCK ISLAND, IL 61299-5001	1
DEFENSE TECHNICAL INFO CENTER ATTN: DTIC-OCP (ACQUISITIONS) 8725 JOHN J. KINGMAN ROAD STE 0944 FT. BELVOIR, VA 22060-6218	2	COMMANDER U.S. ARMY TANK-AUTMV R&D COMMAND ATTN: AMSTA-DDL (TECH LIBRARY) WARREN, MI 48397-5000	1
COMMANDER U.S. ARMY ARDEC ATTN: AMSTA-AR-AEE, BLDG. 3022	1	COMMANDER U.S. MILITARY ACADEMY ATTN: DEPARTMENT OF MECHANICS WEST POINT, NY 10966-1792	1
AMSTA-AR-AES, BLDG. 321	1	U.S. ARMY MISSILE COMMAND	
AMSTA-AR-AET-O, BLDG. 183	1	REDSTONE SCIENTIFIC INFO CENTER	2
AMSTA-AR-FSA, BLDG. 354	1	ATTN: AMSMI-RD-CS-R/DOCUMENTS	
AMSTA-AR-FSM-E	1	BLDG. 4484	
AMSTA-AR-FSS-D, BLDG. 94	1	REDSTONE ARSENAL, AL 35898-5241	
AMSTA-AR-IMC, BLDG. 59	2		
PICATINNY ARSENAL, NJ 07806-5000		COMMANDER U.S. ARMY FOREIGN SCI & TECH CENTER ATTN: DRXST-SD 220 7TH STREET, N.E. CHARLOTTESVILLE, VA 22901	1
DIRECTOR U.S. ARMY RESEARCH LABORATORY ATTN: AMSRL-DD-T, BLDG. 305 ABERDEEN PROVING GROUND, MD 21005-5066	1	COMMANDER U.S. ARMY LABCOM, ISA ATTN: SLCIS-IM-TL 2800 POWER MILL ROAD ADELPHI, MD 20783-1145	1
DIRECTOR U.S. ARMY RESEARCH LABORATORY ATTN: AMSRL-WT-PD (DR. B. BURNS) ABERDEEN PROVING GROUND, MD 21005-5066	1		

NOTE: PLEASE NOTIFY COMMANDER, ARMAMENT RESEARCH, DEVELOPMENT, AND ENGINEERING CENTER,
BENÉT LABORATORIES, CCAC, U.S. ARMY TANK-AUTOMOTIVE AND ARMAMENTS COMMAND,
AMSTA-AR-CCB-O, WATERVLIET, NY 12189-4050 OF ADDRESS CHANGES.

TECHNICAL REPORT EXTERNAL DISTRIBUTION LIST (CONT'D)

	<u>NO. OF COPIES</u>		<u>NO. OF COPIES</u>
COMMANDER U.S. ARMY RESEARCH OFFICE ATTN: CHIEF, IPO P.O. BOX 12211 RESEARCH TRIANGLE PARK, NC 27709-2211	1	WRIGHT LABORATORY ARMAMENT DIRECTORATE ATTN: WL/MNM EGLIN AFB, FL 32542-6810	1
DIRECTOR U.S. NAVAL RESEARCH LABORATORY ATTN: MATERIALS SCI & TECH DIV WASHINGTON, D.C. 20375	1	WRIGHT LABORATORY ARMAMENT DIRECTORATE ATTN: WL/MNMF EGLIN AFB, FL 32542-6810	1

NOTE: PLEASE NOTIFY COMMANDER, ARMAMENT RESEARCH, DEVELOPMENT, AND ENGINEERING CENTER,
BENÉT LABORATORIES, CCAC, U.S. ARMY TANK-AUTOMOTIVE AND ARMAMENTS COMMAND,
AMSTA-AR-CCB-O, WATERVLIET, NY 12189-4050 OF ADDRESS CHANGES.

DEPARTMENT OF THE ARMY

ARMAMENT RESEARCH, DEVELOPMENT AND ENGINEERING CENTER

BENÉT LABORATORIES, CCAC

US ARMY TANK-AUTOMOTIVE AND ARMAMENTS COMMAND

WATERVLIET, N.Y. 12189-4050

OFFICIAL BUSINESS

AMSTA-AR-CCB-O

TECHNICAL LIBRARY